

COMPARISON OF FIBRES PROPERTIES OF AZADIRACHTA INDICA AND ACACIA ARABICA PLANT FOR LIGHTWEIGHT COMPOSITE APPLICATIONS

POREĐENJE OSOBINA VLAKANA BILJAKA AZADIRACHTA INDICA I ACACIA ARABICA ZA PRIMENE KOD LAKIH KOMPOZITA

Originalni naučni rad / Original scientific paper

UDK /UDC: 674.031.746.413.018.9

Rad primljen / Paper received: 3.11.2017

Adresa autora / Author's address:

¹⁾ Department of Mechanical Engineering, Kamaraj College of Engineering and Technology, Virudhunagar, Tamil Nadu, India

²⁾ Department of Mechanical Engineering, Ramaiah Institute of Technology, Bengaluru, Karnataka, India

³⁾ Department of Mechanics, Mathematics and Management, Politecnico di Bari, Bari, Italy, email: claudia.barile@poliba.it

Keywords

- Azadirachta Indica
- Acacia Arabica
- physical analysis
- chemical analysis
- X-ray diffraction
- Fourier transform-infrared spectroscopy
- thermogravimetric analysis
- SEM

Abstract

In this paper, the bark of Azadirachta Indica and Acacia Arabica plant is analysed for investigating and comparing. The aim is to investigate the potential use of these fibres as reinforcements in polymeric materials. The physicochemical properties of Azadirachta Indica fibres (AIFs) and Acacia Arabica fibres (AAF) are examined by chemical constitutions, X-ray diffraction, thermogravimetry analysis, Fourier transform infrared spectroscopy analysis, and surface morphological analysis. AIF has a cellulose content of 68.42 wt.%, density of 740 kgm^{-3} , crystallinity index of 65.04%; AAF has a cellulose content up to 68.1 wt.%, density equal to 1028 kgm^{-3} and crystallinity index of 51.72% respectively. The maximum peak temperature obtained in differential thermogravimetry (DTG) curve is 321.2°C for AIF, and 345.1°C for AAF. The physicochemical results confirm the structural application of AIF and AAF for several industrial fields.

INTRODUCTION

Recently, growing environmental care and sustainability needs throughout the world have increased the attention of researchers to search for better alternatives to synthetic fibres (such as glass, carbon and aramids) /1-4/. Referring to environmental aspects in fact, these synthetic fibres have some disadvantages /5/, but fortunately nature always comes in handy for providing several good alternative materials /6/. These difficulties are overcome by good fibres yielding plants which are cost-effective without compromising mechanical properties. The applications of natural fibres are growing in many sectors such as aerospace, automotive, construction, and packaging industries /7-8/. This is mainly due to their excellent features com-

Ključne reči

- Azadirachta Indica
- Acacia Arabica
- fizička analiza
- hemijska analiza
- Rentgenska difrakcija
- Furijeova transformacija-infracrvena spektroskopija
- termogravimetrijska analiza
- SEM

Izvod

U radu su date analize kora biljaka Azadirachta Indica i Acacia Arabica radi istraživanja i poređenja. Cilj je da se istraži potencijalna primena ovih biljnih vlakana kao ojačanja u kompozitnim materijalima. Fizikohemijske osobine vlakana Azadirachta Indica (AIFs) i vlakana Acacia Arabica (AAF) dobijene su ispitivanjem hemijskog sastava, Rentgenskom difrakcijom, termogravimetrijskom analizom, Furijeovom transformacijom – infracrvenom spektroskopijom i analizom morfologije površine. AIF ima celulozni sastav 68,42 % tež., gustina je 740 kgm^{-3} , indeks kristaliteta 65,04%; AAF ima celulozni sastav do 68,1% tež., gustina je 1028 kgm^{-3} , i indeks kristaliteta 51,72%. Najveća dostignuta temperatura na krivoj diferencijalne termogravimetrije (DTG) jeste $321,2^\circ\text{C}$ za AIF i $345,1^\circ\text{C}$ za AAF. Fizikohemijski rezultati potvrđuju strukturnu primenu AIF i AAF kod nekoliko industrijskih primena.

pared to synthetic fibres, i.e., low cost, low density, cost-effectiveness, high toughness, non-toxic, renewable, recyclable, non-abrasive and biodegradable properties /9-13/. The chemical constituents of bark fibres are strongly dependent on the age, local environmental conditions of the plants /14/. Natural fibres can be extracted from different parts of plants such as stems, leaves, roots, fruits, and seeds. Among all the plant fibres, bark fibres are longer and possess highest degree of compatibility between fibre and matrix. Fibre extracts from the bark of Acacia planifrons, Prosopis juliflora, Grewia optiva, Grewia tillifolia, Cordia dichotoma, Sterculia urens, Acacia leucophloea, and Thespesia lampas proved as evidence for good reinforcements in polymer composites /2, 4, 13, 15-21/.

Azadirachta Indica, well known as Neem tree is pertaining to the mahogany family Meliaceae. It is native in India and it typically grows in tropical and semi-tropical regions. Numerous products made from Azadirachta Indica have been used in India over two millennia because of its inherent medicinal properties. The inter-node length, width, and thickness of average untreated AIF were found to be around 120 mm, 1.27 mm and 1.84 mm, respectively /22/. Acacia Arabica plant was brought to India in 1860 as fuel wood, as the native trees in India in arid and semiarid regions could not fulfil the demands for fuel. It had the capacity to grow in all climatic conditions except in the frost zones of the Himalayan region. It could survive where the annual rainfall was between 150 and 750 mm and maximal temperature 40-45°C and also, they can survive without water for several months /23/. These fibres can be used for making green composites which will be helpful in the applications like light weight sports goods, roofing sheets, door panels, furniture panels, storage tanks, bath units, chairs, partitions, trays, tables, etc /8/.

A pycnometer is used to assess the density of fibres and a chemical analysis is performed to determine their lignin, cellulose, wax, moisture and ash content. The chemical analyses of Azadirachta Indica (AI) and Acacia Arabica (AA) fibres are determined, using X-ray diffraction (XRD) and Fourier transform infrared (FTIR) analysis. The thermal degradation properties are investigated, using thermogravimetric analysis (TGA). A microscopic examination is carried out with a scanning electron microscope (SEM).

MATERIALS AND METHODS

Materials

The fresh and seasoned barks of *A. Indica* are collected in K. Vellakulam village, situated near Kallikudi in Thirumangalam Taluk, Madurai district, Tamil Nadu, India, Fig. 1(a). The barks of *A. Arabica* are collected in Lakshmi-puram, Tirumangalam Taluk, Madurai district of Tamil Nadu, India, Fig. 1(b). The barks of the plant are submerged in water for a maximum period of 3 weeks to allow microbial degradation, and the fibres are extracted by water-retting processes. The fibres are segregated from the degraded barks with a metal teeth brush and thoroughly washed in fresh water. Then the extracted fibres are dried for 1 week at atmospheric temperature to allow maximal removal of moisture for further testing, /6/.

Physical Analysis

The fibres cross-section and their microstructural characteristics and density are presented in this section. SEM is used to analyse the fibres cross-section. Their dimension is calculated by considering the images of a primary and secondary wall of fibres, by means of an image processing software (Image J, NIST) using the SEM images, /24/. The average cross-section diameter is determined by using the 100 mm fibre length considering at least 5 SEM images, /24/. The fibres density is estimated by pycnometer (Mettler Toledo xsz05 balances) for solids by means of an immer-



Figure 1. a) Azadirachta Indica tree, and b) Acacia Arabica tree.

sion liquid known as the Toulon. Initially, the fibres are dried for 48 h in an impermeable no hygroscopic desiccator containing calcium chloride; then impregnated in Toulon for 2 h to remove the microbubbles present in the fibres before measuring the density of the fibres. The fibres are chopped into length of 10 mm and kept into the pycnometer /25/. The fibres density, ρ_{Fibres} , is calculated by the following equation, /25-28/:

$$\rho_{Fibers} = \frac{m_2 - m_1}{(m_3 - m_1)(m_4 - m_2)} \rho_T, \quad (1)$$

where: m_1 is the mass of the empty pycnometer (kg); m_2 is the mass of the pycnometer filled with chopped fibres (kg); m_3 is the mass of the pycnometer filled with Toulon (kg); and m_4 is the mass of the pycnometer filled with chopped fibres and Toulon solution (kg).

Chemical Analysis

The fibres density is evaluated using the Mettler Toledo xsz05 balances method /25/, and its wax content is calculated by Conrad's method, /29/. The chemical composition of fibres cellulose, hemicelluloses, lignin and ash content is determined by standard test methods, /30-31/.

CHARACTERIZATION METHODS

X-ray diffraction (XRD) analysis

Today the use of X-ray techniques for qualitative and quantitative examination of materials is very useful in view of the scatter, emission and absorption properties of X-radiation (X-ray). The phase identification of fibres can be done by XRD analysis. This analysis is carried out by means of a Bruker Eco D8 Advance AXS system. An X-ray tube generates monochromatic intensity of Cu K α radiation in the 10° to 80° range at a scan speed of 5 °/min. The generator works at 40 kV and 30 mA. The crystallinity index (CI) is assessed through the following equation, /32-33/:

$$I_c = \left(1 - \frac{I_{am}}{I_{002}} \right) \times 100\%, \quad (2)$$

where: I_{002} is the intensity of crystalline peak; and I_{am} is the intensity of amorphous peak in the XRD spectrum. The crystallite size (CS) of the fibres is worked out by the following equation:

$$CS = \frac{K\lambda}{\beta \cos \theta} \quad (3)$$

where: $K = 0.89$ is Scherrer's constant; β symbolizes the peak's full-width at half-maximum; and λ denotes the wavelength of the radiation.

Fourier transform-infrared (FTIR) analysis

FTIR spectrum of fibres is recorded by using Shimadzu spectrometer (FTIR-8400S, Japan) to determine the presence of free functional groups on the fibres. In this analysis, powdered fibre sample of potassium bromide (KBr) pellets are used. The FTIR spectrum was recorded in the range of 4000-500 cm^{-1} region at a temperature of 30 °C and at 65% humidity. The spectrum is identified with a scanning rate of 32 scans $\cdot\text{min}^{-1}$ to achieve an acceptable signal-to-noise ratio with a resolution of 2 cm^{-1} .

Thermogravimetric analysis

Thermogravimetric analysis measures the amount of fibres weight changes as a function of increasing temperature in an atmosphere of nitrogen. Thermal stability of the fibres is analysed by TGA using a Jupiter simultaneous thermal analyser (Model STA 449 F3, Netzsch, Germany), by studying the weight loss and transformation. The measurement is performed in high purity nitrogen atmosphere at a flow rate of 20 $\text{mL}\cdot\text{min}^{-1}$, and the weight loss is recorded at a heating rate of 10 °C $\cdot\text{min}^{-1}$ in the temperature range of 30-600 °C. Measurements are made by using an alumina crucible to maintain a good contact between the sample and thermocouple.

Surface morphological analysis by SEM

A scanning electron microscopy (Carl Zeiss EVO 18) was operated with an accelerated voltage of 20 kV and magnification of 300 \times for fibres visualization. In order to avoid the accumulation of electrical charges during analysis, the sample is covered with a thin gold layer.

RESULTS AND DISCUSSION

Physical analysis

The fibres cross-section of both AI and AF are approximately round in shape and used to determine the diameter of the fibre. The fibre cross-section varied by varying fibres length and they are determined by SEM at various location. Five samples are used to measure the diameter of the fibre at four points with equal spacing through 100 to 1000 mm long fibres. The fibre diameter evaluated is up to 40-250 μm and 30-180 μm for AIF and AAF, respectively. Figure 2 shows the SEM images of AIF and AAF.

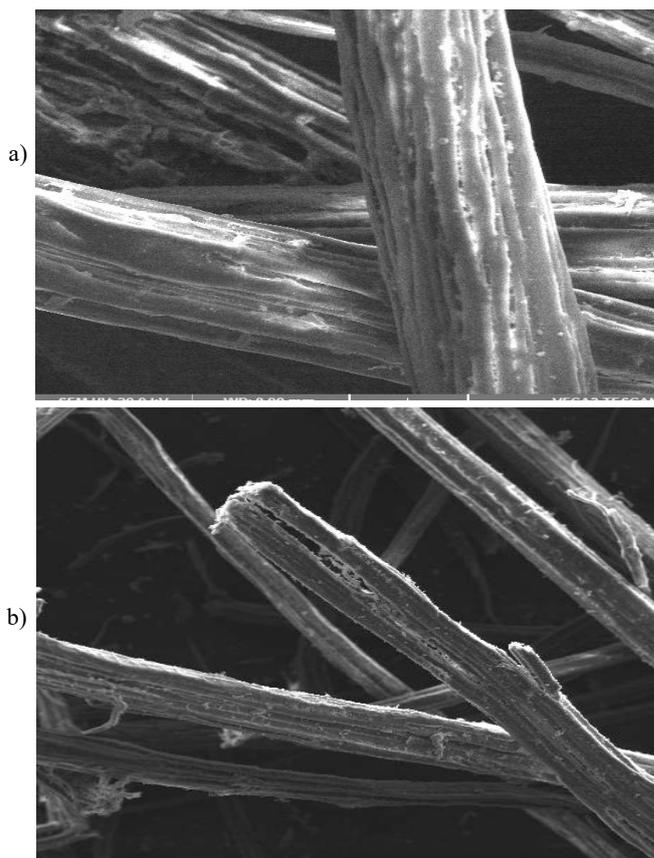


Figure 2. SEM images of the longitudinal section of: a) AIF and b) AAF.

Chemical analysis

The chemical composition of fibres is compared with various other bark fibres reported in scientific literature and listed in Table 1. The chemical composition of the fibres, cellulose, hemicellulose and lignin are strongly affected by the age of the plant, soil characteristics, extraction conditions and methods used to determine the composition, /34/. The assessed AIFs cellulose (68.42 wt.%) is better than AAFs cellulose (68.1 wt.%), but both of them are greater than other bark natural fibres such as Prosopis juliflora (61.65 wt.%), Cordia dichotoma (59.7 wt.%), Grewia tiliifolia (62.8 wt.%), and Oil palm empty fruit bunch (41 wt.%) /2, 16, 17, 35/. Usually, fibres tensile strength and Young's modulus are proportional to the cellulose content, /36-37/. The hemicellulose content of AIFs is equal to 13.72%; its degradation usually leads to fibres collapse into

Table 1. Comparison of chemical compositions of raw AIFs and AAFs with various natural fibres.

Fibre name	Cellulose (wt.%)	Hemicelluloses (wt.%)	Lignin (wt.%)	Wax (wt.%)	Moisture content (%)	Density (kg/m ³)	Ash (wt.%)
AIFs	68.42	13.72	13.58	0.43	-	740	-
AAFs	68.10	9.36	16.86	0.49	-	1028	-
Acacia planifrons	73.1	9.41	12.04	0.57	8.21	660	4.06
Prosopis juliflora	61.65	16.14	17.11	0.61	9.48	580	5.2
Sansevieria cylindrica	79.7	10.13	3.8	0.09	3.08	915	-
Cyperus pangorei	68.5		17.88	0.17	9.19	1102	-
Grewia Tilifolia	62.80	21.20	14.90	-	2.3	-	-
Oil palm empty fruit bunch	65	29	17.5	4	-	-	-
Henequen	60	28	8	0.5	-	-	-
Agave	68.42	4.85	4.85	0.26	7.69	1200	-
Sansevieria ehrenbergii	80	11.25	7.8	0.45	10.55	887	0.6

cellulose microfibrils resulting in lower strength due to the linking effect. Hemicellulose content (9.36 wt.%) of the AAFs is considered a compatibilizer between cellulose and lignin. The lignin content of AIFs is 13.58 % and it influences the fibre structure, properties, and morphology. Higher lignin content is evaluated for AAFs (16.86 wt.%). It saves water in the fibres, acting as a protection against biological attack and contributing to the fibres structure and morphology; it provides good rigidity compared to the other fibres too, /38/. The lowest wax content is evaluated for AIFs (0.43 %). It affects the interfacial bond between fibres and matrix during fabrication. Therefore, to improve the interfacial bonding between the AIFs and resin, fibres chemical treatment has to be done in order to remove the wax and moisture content, /25/. However, AAFs contain endurable wax (0.49 wt.%), which may lead to poor interfacial bonding between fibres and polymer matrices, /19/. Of significance are both densities, 740 kgm⁻³ for the AIFs, and 1028 kgm⁻³ for AAFs. This analysis reveals that AIFs will be much useful to make light-weight composite structures.

X-ray diffraction (XRD) analysis

Figure 3 presents X-ray diffraction pattern of AIFs and AAFs. It displays two clear diffraction peaks at 2 θ : 15.03° and 22.64° for AIFs, and 22.45° and 15.08° for AAFs, which are commonly witnessed for natural fibres. In AIFs, the peak 15.03° reveals the occurrence of non-cellulosic materials such as hemicellulose, amorphous cellulose, pectin and lignin in the fibres, while the peak 22.64° indicates the content of cellulose in the fibre, /37/. However, in AAFs, the minimal intensity peak is observed at 18.39°, which contains a higher percentage of amorphous fraction (lignin, pectins, hemicellulose, and amorphous cellulose). The calculated CI for AIFs is 65.04 % and CI for AAFs is 51.72 % which are much higher than that of Prosopis juliflora (46 %) and Acacia leucophloea (51 %), and lower than that of Acacia planifrons (65.38 %), jute (71 %) and hemp (88 %) fibres, /13/. The crystallite size (CS) of AIFs is estimated by Scherer's formula as specified in Eq.(2) and the value of CS is found to be 2.75 nm. CS in AIFs poses chemical reactivity and water absorption capacity properties. Besides, the CS of the AAFs estimated as 15 nm reduces the water absorption capacity and chemical reactivity of the fibre, yet it is comparable to that of flax fibre (2.8 nm) and quite close to that of ramie fibre (16 nm). This result reveals that these fibres will be used when cost

reduction is the prime consideration, and can effectively replace the relatively expensive materials.

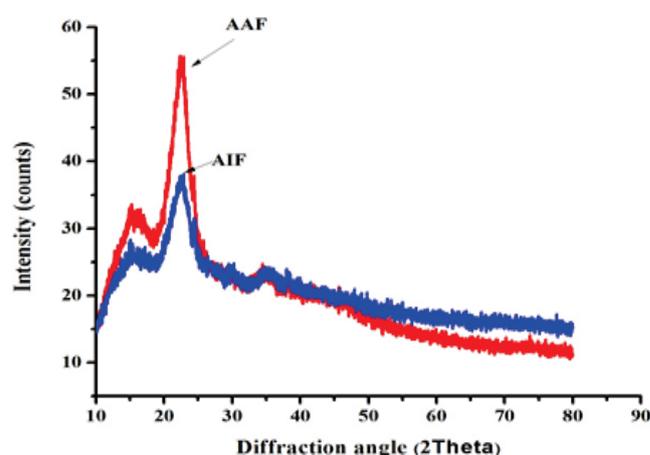


Figure 3. X-ray diffractogram of AIFs and AAFs.

Fourier transform-infrared (FTIR) analysis

Figure 4 summarizes the functional groups of the AIFs spectrum in the range of wave numbers from 4000 to 500 cm⁻¹. The FTIR spectrum shows absorption bands of different chemical groups of bio-fibre components such as cellulose, hemicellulose and lignin. The major components are alkenes, phenolic hydroxyl group, aromatic groups, and several functional groups having oxygen (ester, ketone and alcohol), /39/. In AIFs, A 'U' shape arises about 3700-3000 cm⁻¹ which are related to the hydrogen bonded O-H (alcohol group) stretching vibration from the cellulose arrangement of the AIFs, /40/. The peak at 2917 cm⁻¹ characteristic bands for the C-H stretching vibration from CH in cellulose and the peak at 2366 cm⁻¹ showed the existence of wax which is allotted to the less ordered band of the alkyl chain. The CH₂ symmetric bending band is estimated at a peak of 1413 cm⁻¹, /41/. The carbonyl region is absorbed in the peak at 1618 cm⁻¹ is allocated to O-H bending vibration in hemicellulose region. The bending vibration C-O group of aromatic ring lignin shows peaks at 1048 cm⁻¹ stretched vibration. However, one of the most noticeable peaks in the AAFs spectrum appeared at 3442 and 1022 cm⁻¹ corresponding to O-H stretching and O-H bending frequencies, respectively, /20/. The two sharp peaks at 2922 cm⁻¹ and 2854 cm⁻¹ are assigned to pronounced C-H stretching vibration of CH and CH₂ in cellulose and hemi-

cellulose components, /42/. The absorption peak at 1741 cm^{-1} is attributed to the carbonyl group stretching vibration of the alpha-keto carboxylic acid in lignin or the ester group in hemicellulose. The carbonyl region is projected at 1700 cm^{-1} and the peak at 1649 cm^{-1} is assigned to C-O stretching vibration of the acetyl group in lignin and hemicellulose. The bending vibration of C-H and C-O group of the aromatic ring of hemicellulose and lignin are observed at 1462 cm^{-1} and 1325 cm^{-1} stretching vibration.

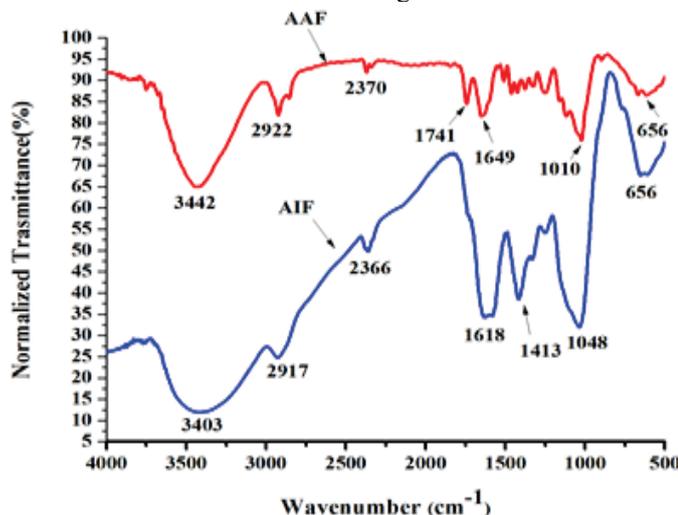


Figure 4. FTIR analysis of AIFs and AAFs.

Thermogravimetric analysis

The thermal stability performance of fibres is investigated using TG curves as shown in Fig. 5. The initial degradation of AIFs is spotted in range from 50 to $230\text{ }^{\circ}\text{C}$, /42/. The second degradation of AIFs developed from the temperature range of $240\text{--}400\text{ }^{\circ}\text{C}$ in which a peak fairly near to $300\text{ }^{\circ}\text{C}$ associated to thermal depolymerization of hemicellulose with 13.54 % of mass loss is detected. Another noticeable peak at $321.2\text{ }^{\circ}\text{C}$ indicates the degradation of cellulose with a foremost weight loss of about 34.51 % /43/. Comparable results are also detected at $331.1\text{ }^{\circ}\text{C}$, $345.1\text{ }^{\circ}\text{C}$ and $333.02\text{ }^{\circ}\text{C}$ for *Prosopis juliflora*, *Acacia Arabica*, *Sansevieria ehrenbergii*, respectively /2, 4, 43/. The ending region from 450 to $500\text{ }^{\circ}\text{C}$ denoted significance of oxidative degradation of the charred residue. The weight loss may be associated with dehydration as well as degradation of lignin content in fibre. Typically, two stages of degradation are observed during the AAFs thermal stability study. The initial degradation noticed (at $84.4\text{ }^{\circ}\text{C}$) between room temperature and $100\text{ }^{\circ}\text{C}$ could be due to the evaporation of moisture present in the AAFs. The second major degradation progressed from the temperature region of $240\text{--}400\text{ }^{\circ}\text{C}$ in which a peak quite close to $300\text{ }^{\circ}\text{C}$ related to thermal depolymerization of hemicellulose with 16.20 % of mass loss is noticed, /38/. A very prominent peak at $345.1\text{ }^{\circ}\text{C}$ showed a major mass loss of about 52.63 % due to the degradation of cellulose. Similar results are also observed at $346.8\text{ }^{\circ}\text{C}$, $331.1\text{ }^{\circ}\text{C}$, $321\text{ }^{\circ}\text{C}$, $308.2\text{ }^{\circ}\text{C}$, $298.2\text{ }^{\circ}\text{C}$ and $309.2\text{ }^{\circ}\text{C}$ for *A. leucophloea*, *P. juliflora*, bamboo, hemp, jute, and Kenaf fibres, respectively, /43/. However, the degradation of the aromatic structure of lignin occurred slowly under the initial temperature up to $600\text{ }^{\circ}\text{C}$, /45/.

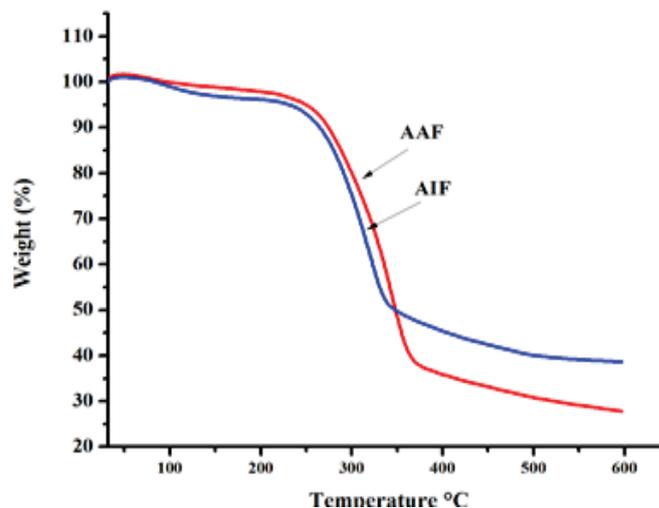


Figure 5. TG curves of AIFs and AAFs.

Surface morphological analysis by SEM

Morphology studies of AIFs and AAFs are carried out using a scanning electron microscope to evaluate the fibre surface structure, Fig. 6(a) and (b). The changes in morphology are significant to forecast the fibre interaction with the polymer matrix in composites. In general, all-natural cellulose fibres are multi-cellular, where lignin and hemicellulose bind a bundle of individual cells, /40/.

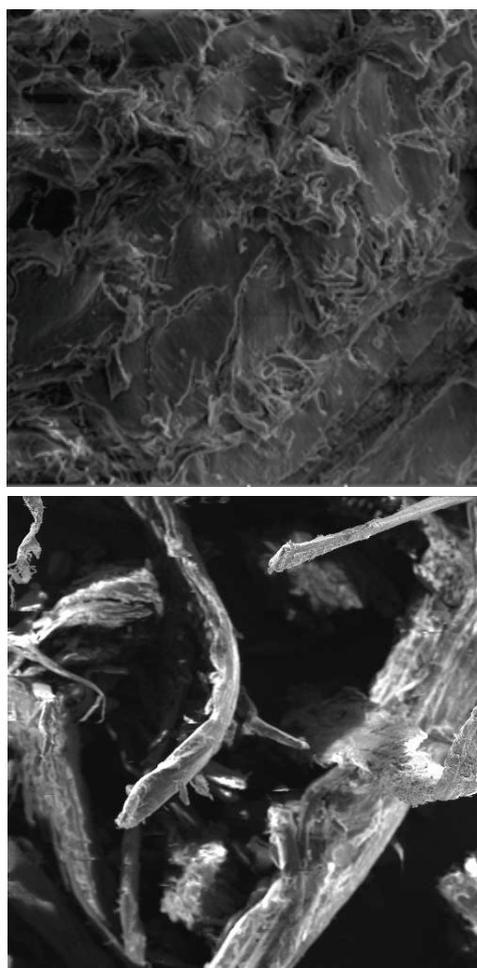


Figure 6 (a). SEM images of cross-section of AIFs.

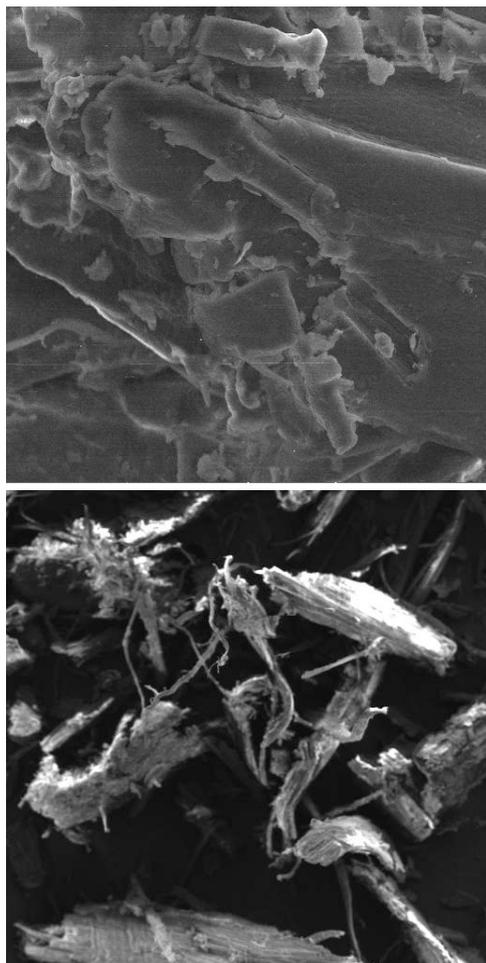


Figure 6 (b). SEM images of cross-section of AFFs.

CONCLUSION

In this investigation, the chemical composition, FTIR analysis, crystalline characteristic, SEM and thermal degradation of AIFs and AAFs are studied. The high amount of cellulose in AIFs and AAFs can provide a relatively high crystallinity index and the lower density of AIFs and AAFs exposed to make them suitable for lightweight composite applications. The thermal stability analysis demonstrated AIFs and AAFs cellulose degradation temperature. The characterization results clearly show that the AIFs and AAFs are a better alternate reinforcement of making composites. These characterization results also confirm its usage of AIFs and AAFs for various applications.

REFERENCES

- Koronis, G., Silva, A., Fontul, M. (2013), *Green composites: A review of adequate materials for automotive applications*, Comp. Part B: Eng. 44(1): 120-127. doi: 10.1016/j.compositesb.2012.07.004
- Saravanakumar, S.S., Kumaravel, A., Nagarajan, T., et al. (2013), *Characterization of a novel natural cellulosic fiber from Prosopis juliflora bark*, Carbohydr. Polym. 92(2): 1928-1933. doi: 10.1016/j.carbpol.2012.11.064
- Sanjay, M.R., Arpitha, G.R., Yogesha, B. (2015), *Study on mechanical properties of natural-glass fibre reinforced polymer hybrid composites: A review*, Mater. Today: Proc. 2(4-5): 2959-2967. doi.org/10.1016/j.matpr.2015.07.264
- Manimaran, P., Saravanakumar, S.S., Mithun, N.K., Senthama-raikannan, P. (2016), *Physicochemical properties of new cellulosic fibers from bark of Acacia Arabica*, Int. J Polym. Anal. Char. 21(6): 548-553. doi.org/10.1080/1023666X.2016.1177699
- Sanchez Nacher, L., Crespo Amoros, J.E., Salvador Moya, M. D., Lopez Martinez, J. (2007), *Mechanical properties of polyester resins in saline water environments*, Int. J Polym. Anal. Charact. 12(5): 373-390. doi.org/10.1080/10236660701516557
- Indran, S., Raj, R.E., Sreenivasan, V.S. (2014), *Characterization of new natural cellulosic fiber from Cissus quadrangularis root*, Carbohydr. Polym. 110: 423-429. doi.org/10.1016/j.carbpol.2014.04.051
- Malkapuram, R., Kumar, V., Negi, Y.S. (2009), *Recent development in natural fibre reinforced polypropylene composites*, J Reinf. Plast. Compos. 28(10):1169-1189. doi.org/10.1177/0731684407087759
- Sanjay, M.R., Arpitha, G.R., Laxmana Naik, L., et al. (2016), *Applications of natural fibers and its composites: An overview*, Nat. Res. 7(3): 108-114. doi: 10.4236/nr.2016.73011
- Mohanty, A.K., Misra, M., Drzal, L.T. (2002), *Sustainable biocomposites from renewable resources: opportunities and challenges in the green materials world*, J Polym. Environ. 10(1-2): 19-26.
- Wambua, P., Ivens, J., Verpoest, I. (2003), *Natural fibers: can they replace glass in fiber reinforced plastics?*, Compos. Sci. Tech. 63(9): 1259-1264. doi:10.1016/S0266-3538(03)00096-4
- Joshi, S.V., Drzal, L.T., Mohanty, A.K., Arora, S. (2004), *Are natural fiber composites environmentally superior to glass fiber reinforced composites?*, Compos. Part A 35(3): 371-376. doi.org/10.1016/j.compositesa.2003.09.016
- Cheung, H.Y., Ho, M.P., Lau, K.T., et al. (2009), *Natural fibre-reinforced composites for bioengineering and environmental engineering applications*, Compos. Part B 40: 655-663. doi:10.1016/j.compositesb.2009.04.014
- Senthamaraiannan, P., Saravanakumar, S.S., Arthanarieswaran, V.P., Sugumaran, P. (2015), *Physicochemical properties of new cellulosic fibers from bark of Acacia planifrons*, Int. J Polym. Anal. Charact. 21(3): 207-213. doi: 10.1080/1023666X.2016.1133138
- Batra, S.K. (1981), Other long vegetable fibres. In Handbook of Fiber Science and Technology. Vol. IV: Fiber Chemistry, Eds. M. Lewin and E.M. Pearce. New York: Marcel Dekker, pp.727-808.
- Singha, A.S., Thakur, V.K. (2009), *Synthesis and characterizations of silane treated Grewia optiva fibers*, Int. J Polym. Anal. Charact. 14(4): 301-321. doi.org/10.1080/10236660902871470
- Jayaramudu, J., Guduri, B.R., Varada Rajulu, A. (2010), *Characterization of new natural cellulosic fabric Grewia tilifolia*, Carbohydr. Polym. 79(4): 847-851. doi.org/10.1016/j.carbpol.2009.10.046
- Jayaramudu, J., Maity, A., Sadiku, E.R., et al. (2011), *Structure and properties of new natural cellulose fabrics from Cordia dichotoma*, Carbohydr. Polym. 86(4): 1623-1629. doi.org/10.1016/j.carbpol.2011.06.071
- Jayaramudu, J., Guduri, B.R., Rajulu, A.V. (2009), *Characterization of natural fabric Sterculia urens*, Int. J Polym. Anal. Charact. 14(2): 115-125. doi: 10.1080/10236660802601415
- Arthanarieswaran, V.P., Kumaravel, A., Saravanakumar, S.S. (2015), *Characterization of new natural cellulosic fiber from Acacia leucophloea bark*, Int. J Polym. Anal. Charact. 20(4): 367-376. doi.org/10.1080/1023666X.2015.1018737
- Obi Reddy, K., Guduri, B.R., Varada Rajulu, A. (2009), *Structural characterization and tensile properties of Borassus fruit fibers*, J Appl. Polym. Sci. 114(1): 603-611. doi.org/10.1002/app.30584

21. Obi Reddy, K., Ashok, B., Raja Narendra Reddy, K., et al. (2014), *Extraction and characterization of novel lignocellulosic fibers from Thespesia lampas plant*, Int. J Polym. Anal. Charact. 19(1): 48-61. doi: 10.1080/1023666X.2014.854520
22. Abbas, B., el-Tayeb, A.E., Sulleiman, Y.R. (1992), *Calotropis procera: feed potential for arid zones*, Veter. Rec. 131(6): 132.
23. Maslin, B.R., Miller, J.T., Seigle, D.S. (2003), *Overview of the generic status of Acacia (Leguminosae: Mimosoideae)*, Aust. Syst. Bot.16(1): 1-18. doi.org/10.1071/SB02008
24. Nayak, R., Padhye, R., Kyratzis, I.L., et al. (2013), *Effect of viscosity and electrical conductivity on the morphology and fiber diameter in melt electrospinning of polypropylene*, Text. Res. J 83(6): 606-617. doi.org/10.1177/0040517512458347
25. Sathishkumar, T.P., Navaneethkrishnan, P., Shankar, S., Rajasekar, R. (2013), *Characterization of new cellulose Sansevieria ehrenbergii fibers for polymer composites*, Compos. Int. 20(8): 575-593. doi.org/10.1080/15685543.2013.816652
26. Murali Mohan Rao, K., Ratna Prasad, A.V., Ranga Babu, M.N.V., et al. (2007), *Tensile properties of elephant grass fiber reinforced polyester composite*, J Mat. Scie. 42(9):3266-3272. doi: 10.1007/s10853-006-0657-8
27. Murali Mohan Rao, K., Mohana Rao, K. (2007), *Extraction and tensile properties of natural fibers: v akka, date and bamboo*, Comp. Struc. 77(3):288-295. doi: 10.1016/j.compstruct.2005.07.023
28. Sathishkumar, T.P., Navaneethkrishnan, P., Shankar, S. (2012), *Tensile and flexural properties of snake grass natural fiber reinforced isophthallic polyester composites*, Compos. Sci. Technol. 72(10):1183-1190. doi.org/10.1016/j.compscitech.2012.04.001
29. Conrad, C.M. (1944), *Determination of wax in cotton fiber, a new alcohol extraction method*, Ind. Eng. Chem. Anal. Ed. 16 (12):745-748. doi: 10.1021/i560136a007
30. Doree, C. (1950), *The Methods of Cellulose Chemistry* (2nd Ed.). London: Chapman and Hall.
31. Liu, L., Cao, J., Huang, J., et al. (2010), *Extraction of pectins with different degrees of esterification from mulberry branch bark*, Biores. Techn. 101(9):3268-3273. doi: 10.1016/j.biortech.2009.12.062
32. Segal, L., Creely, J.J., Martin, A.E. Jr., Conrad, C.M. (1959), *An empirical method for estimating the degree of crystallinity of native cellulose using X-ray diffractometer*, Text. Res. J 29 (10):786-794. doi.org/10.1177/004051755902901003
33. Yuan, P., Annabi-Bergaya, F., Tao, Q., et al. (2008), *A combined study by XRD, FTIR, TG and HRTEM on the structure of delaminated Fe-intercalated/pillared clay*, J Coll. Interf. Scie. 324(1-2):142-149. doi: 10.1016/j.jcis.2008.04.076
34. Maepa, C.E., Jayaramudu, J., Okonkwo, J.O., Ray, S.S., et al. (2015), *Extraction and characterization of natural cellulose fibers from Maize tassel*, Int. J Polym. Anal. Charact. 20(2): 99-109. doi.org/10.1080/1023666X.2014.961118
35. Shaji, J., Kuruvilla, J., Sabu, T. (2006), *Green composites from natural rubber and oil palm fiber: physical and mechanical properties*, Int. J Polym. Mater. Polymer. Biomater. 55(11): 925-945. doi.org/10.1080/00914030600550505
36. Kathiresan, M., Pandiarajan, P., Senthamarikannan, P., Saravanakumar, S.S. (2016), *Physicochemical properties of new cellulosic Artisdita hystrix leaf fiber*, Int. J Polym. Anal. Charact. 21(8):663-668. doi.org/10.1080/1023666X.2016.1194636
37. Prithiviraj, M., Muralikannan, R., Senthamarikannan, P., Saravanakumar, S.S. (2016), *Characterization of new natural cellulosic fiber from the Perotis Indica plant*, Int. J Polym. Anal. Charact. 21(8):669-674. doi.org/10.1080/1023666X.2016.1202466
38. Saravanakumar, S.S., Kumaravel, A., Nagarajan, T., et al. (2013), *Characterization of a novel natural cellulosic fiber from Prosopis juliflora bark*, Carbohydr. Polym. 92(2):1928-1933. doi: 10.1016/j.carbpol.2012.11.064
39. Burgueno, R., Quagliata, M.J., Mehta, G.M., et al. (2005), *Sustainable cellular biocomposites from natural fibers and unsaturated polyester resin for housing panel applications*, J Polym. Envir. 13(2):139-149. doi: 10.1007/s10924-005-2945-9
40. Obi Reddy, K., Uma Maheswari, C., Muzenda, E., et al. (2016), *Extraction and characterization of cellulose from pre-treated ficus (Peepal tree) leaf fibers*, J Nat. Fib. 13(1):54-64. doi.org/10.1080/15440478.2014.984055
41. Thamae, T., Baillie, C. (2007), *Influence of fiber extraction method, alkali and silane treatment on the interface of Agave Americana waste HDPE composites as possible roof ceilings in Lesotho*, Comp. Interf. 14(7-9):821-836. doi.org/10.1163/156855407782106483
42. Kommula, V.P., Obi Reddy, K., Shukla, M., et al. (2013), *Physico-chemical, tensile, and thermal characterization of Napier grass (native African) fiber strands*, Int. J Polym. Anal. Charact. 18(4): 303-314. doi.org/10.1080/1023666X.2013.784935
43. Yao, F., Wu, Q., Lei, Y., et al. (2008), *Thermal decomposition kinetics of natural fibers: activation energy with dynamic thermogravimetric analysis*, Polym. Degrad. Stab. 93(1): 90-98. doi.org/10.1016/j.polyimdeggradstab.2007.10.012
44. Yang, P, Kokot, S. (1996), *Thermal analysis of different cellulosic fabrics*, J Appl. Polym. Sci. 60(8): 1137-1146. doi.org/10.1002/(SICI)1097-4628(19960523)60:8<1137::AID-APP6>3.0.CO;2-M

© 2018 The Author. Structural Integrity and Life, Published by DIVK (The Society for Structural Integrity and Life 'Prof. Dr Stojan Sedmak') (<http://divk.inovacionicentar.rs/ivk/home.html>). This is an open access article distributed under the terms and conditions of the [Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International License](#)